




The Effect of Radiation on Selected Photographic Film

Richard Slater
Lyndon B. Johnson Space Center
Houston, Texas 77058-3696

John Kinard
Lyndon B. Johnson Space Center
Houston, Texas 77058-3696

Ivan Firsov
Energia Space Corporation
Moscow, Russia

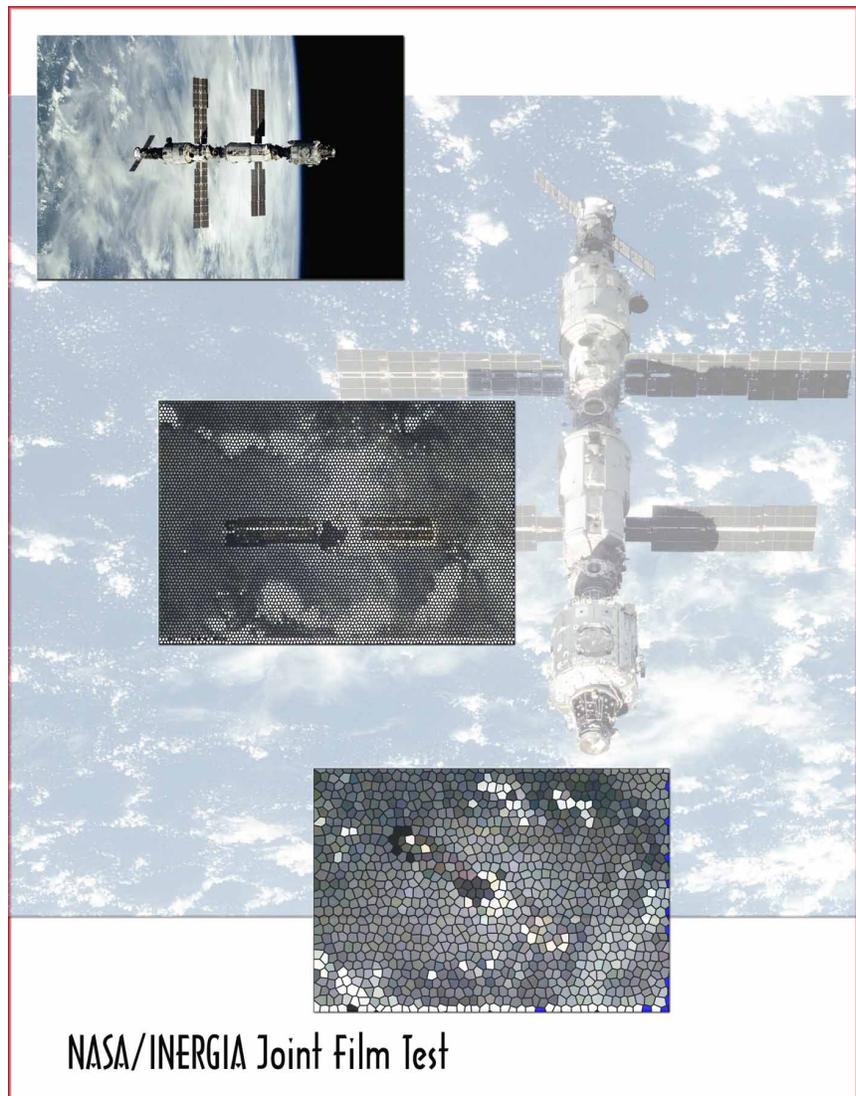

The NASA STI Program Office ... in Profile

Since its founding, NASA has been dedicated to the advancement of aeronautics and space science. The NASA Scientific and Technical Information (STI) Program Office plays a key part in helping NASA maintain this important role.

The NASA STI Program Office is operated by Langley Research Center, the lead center for NASA's scientific and technical information. The NASA STI Program Office provides access to the NASA STI Database, the largest collection of aeronautical and space science STI in the world. The Program Office is also NASA's institutional mechanism for disseminating the results of its research and development activities. These results are published by NASA in the NASA STI Report Series, which includes the following report types:

- **TECHNICAL PUBLICATION.** Reports of completed research or a major significant phase of research that present the results of NASA programs and include extensive data or theoretical analysis. Includes compilations of significant scientific and technical data and information deemed to be of continuing reference value. NASA counterpart of peer-reviewed formal professional papers, but having less stringent limitations on manuscript length and extent of graphic presentations.
- **TECHNICAL MEMORANDUM.** Scientific and technical findings that are preliminary or of specialized interest, e.g., quick release reports, working papers, and bibliographies that contain minimal annotation. Does not contain extensive analysis.
- **CONTRACTOR REPORT.** Scientific and technical findings by NASA-sponsored contractors and grantees.


- **CONFERENCE PUBLICATION.** Collected papers from scientific and technical conferences, symposia, seminars, or other meetings sponsored or co-sponsored by NASA.
- **SPECIAL PUBLICATION.** Scientific, technical, or historical information from NASA programs, projects, and missions, often concerned with subjects having substantial public interest.
- **TECHNICAL TRANSLATION.** English-language translations of foreign scientific and technical material pertinent to NASA's mission.

Specialized services that complement the STI Program Office's diverse offerings include creating custom thesauri, building customized databases, organizing and publishing research results ... even providing videos.

For more information about the NASA STI Program Office, see the following:

- Access the NASA STI Program Home Page at <http://www.sti.nasa.gov>
- E-mail your question via the Internet to help@sti.nasa.gov
- Fax your question to the NASA STI Help Desk at (301) 621-0134
- Telephone the NASA STI Help Desk at (301) 621-0390
- Write to:
NASA STI Help Desk
NASA Center for AeroSpace Information
7121 Standard Drive
Hanover, MD 21076-1320

NASA/TP—2000—210193



The Effect of Radiation on Selected Photographic Film

Richard Slater
Lyndon B. Johnson Space Center
Houston, Texas 77058-3696

John Kinard
Lyndon B. Johnson Space Center
Houston, Texas 77058-3696

Ivan Firsov
Energia Space Corporation
Moscow, Russia

National Aeronautics and
Space Administration

Lyndon B. Johnson Space Center
Houston, Texas 77058

October 2000

Available from:

NASA Center for AeroSpace Information
7121 Standard Drive
Hanover, MD 21076-1320
301-621-0390

National Technical Information Service
5285 Port Royal Road
Springfield, VA 22161
703-605-6000

This report is also available in electronic form at <http://techreports.larc.nasa.gov/cgi-bin/NTRS>

CONTENTS

	Page
CONTENTS	iii
ACRONYMS.....	iv
ABSTRACT	1
1.0 INTRODUCTION	1
2.0 TEST PROCEDURE.....	3
2.1 Sensitometric Film Preparation.....	3
2.2 Standard Scene Imagery Preparation	3
2.3 Packaging and Storage of Film Samples	4
2.4 Film Processing	4
2.5 Digital Processing.....	4
3.0 EVALUATION CRITERIA.....	5
4.0 IMAGERY ANALYSIS.....	5
4.1 Visual Evaluation	6
4.1.1 Image Contrast.....	6
4.1.2 Color Rendition	6
4.1.3 Shadow and Highlight Detail	6
4.2 Sensitometric Evaluation.....	7
4.2.1 Film Speed.....	7
4.2.2 Average Gradient.....	7
4.2.3 Log Exposure Range	7
4.2.4 Useful Density Range.....	8
4.3 Digital Evaluation.....	8
4.3.1 Grain Analysis	8
4.3.2 Color Shift Analysis	8
4.3.3 Color Layer Analysis.....	8
5.0 RESULTS.....	9
5.1 Comparison of Sensitometric Data for All Control and 120-Day Test Samples	9
5.2 Test Film Templates.....	12
6.0 CONCLUSIONS	24

Tables

Table 1. Speed.....	10
Table 2. Average Gradient	10
Table 3: Log Exposure Range.....	11
Table 4. Density Range.....	11

ACRONYMS

ISO	International Organization of Standardization
ISS	International Space Station
JSC	Johnson Space Center
STS	Space Transportation System (Shuttle mission)

ABSTRACT

We conducted this film test to evaluate several manufacturers' photographic films for their ability to acquire imagery on the International Space Station. We selected 25 motion picture, photographic slide, and negative films from three different film manufacturers. We based this selection on the fact that their films ranked highest in other similar film tests, and on their general acceptance by the international community. This test differed from previous tests because the entire evaluation process leading up to the final selection was based on information derived after the original flight film was scanned to a digital file. Previously conducted tests were evaluated entirely based on 8x10s that were produced from the film either directly or through the internegative process. This new evaluation procedure provided accurate quantitative data on granularity and contrast from the digital data. This test did not try to define which film was best visually. This is too often based on personal preference. However, the test results did group the films by good, marginal, and unacceptable. We developed, and included in this report, a template containing quantitative, graphical, and visual information for each film. These templates should be sufficient for comparing the different films tested and subsequently selecting a film or films to be used for experiments and general documentation on the International Space Station.

1.0 INTRODUCTION

The level of radiation encountered in space is greater than that found at the surface of the Earth. High background levels of radiation damage unprocessed photographic materials, which are typically somewhat sensitive to nonvisible portions of the electromagnetic spectrum.

The absorption of radiation by photographic films causes photographic fog. Fog occurs when photographic materials absorb uniform levels of energy that is part of an intended photographic exposure. Fog affects the coarsest portions of the photographic media that comprise the most light-sensitive portions of films. In negative materials, fog raises the resultant density of the toe of the sensitometric curve. The toe is the portion of the curve that has the first response to light and determines the overall film speed. Fog results in a decrease in the tonal ranges of the photographic response, and of the densities produced for printing results. Most of this lowered contrast is in the less-well-illuminated parts of the photographed scene. As a result, detail there may be absent in the final imagery. In reversal films the fastest grains are also affected, but these are subsequently removed in the processing of the film and any losses in contrast occur in the brightest parts of the scene where contrast is less perceivable.

The purpose of this test is to measure the degree of film degradation caused by radiation and find methods of reversing these effects for both visual and scientific applications. It also augments previous tests conducted on both the Russian space station *Mir* and the Space Shuttle. A test flown in September 1991 on board Shuttle mission (STS)-48 showed that positive film

(preferably low speed) is superior to negative film, a standard lead-lined film bag will not prevent radiation damage, and there is no place in the Shuttle that offers any real protection from radiation. A subsequent film test flown in 1994 on board *Mir* benchmarked how radiation effects routinely flown flight film when left in orbit for a period of 120 days. The 120 days was intended to represent a standard *Mir* or International Space Station (ISS) increment. This test used new technology films available at the time and added a visual image to the test. This resulted in providing visual information on how films would be effected on orbit and established that Kodak Gold 200 did the best job of any negative film. This was significant because previous testing concluded that lower film speeds delivered better results. Kodak Gold 200 fell into the medium-range-speed films.

We intended that this radiation film test would be more comprehensive and would provide some methods for correcting the damage to the film from the effects of radiation. We made several major changes to the scope of this test. We added Agfa and Fuji films to the Kodak films used in the first test, and increased the number of different film speeds tested (ASA 50 to 650, in both positive and negative form). We also tested for a range of time periods that parallel how the film will be used on *Mir* and the ISS, and provided quantitative and qualitative evaluation data on the effects of radiation on each film sample.

Our intention for including Agfa and Fuji film types was to provide a selection of films that scientists from the international scientific community are currently using. A major objective was to determine the threshold at which a film begins to exhibit enough damage from radiation that it compromises its value to the experiment. Another objective was to determine whether each film had a radiation damage limit. Ivan Firsov of the Energia Space Corporation proposed the time period for this experiment. His experience using various types of film on *Mir* led us to vary the time period for the experiment to between 30 and 120 days. He concluded from his own experience that 30 days was the smallest period of time that would cause any significant damage and that, after 90 days, there is a plateau in the damage. For this reason, three sample sets were flown for periods of 39, 63, and 120 days. The 120-day test was included to support the theory that a plateau can be seen at 120 days. Flight constraints did not allow for the 90-day test and modified the 30 and 60 day test periods. This is the first radiation film test to incorporate primarily digital procedures for qualifying and quantifying the image degradation due to radiation. The primary reasons for changing from an analog to digital procedure were the availability of off-the-shelf software using digital files, and the fact that image distribution is primarily digital for human spaceflight using the Intranet and Internet.

2.0 TEST PROCEDURE

This test procedure describes the preparation and testing of the selected films that were flown on a collaborative mission between NASA and the Energia Space Corporation. The three categories of films tested are ECN motion picture films, E-6, and C-41. The films that were tested include:

ECN: Fuji 8521 F64D and Kodak 5293

E-6: Agfa Agfachrome RSX 50, Agfa Agfachrome RSX 100, Agfa Agfachrome RSX 200, Fuji Provia RDP2, Fuji Provia RHP, Fuji Velvia RVP, Kodak 5017 Ektachrome, Kodak 5069 Elite 100S, and Kodak 5075 Elite 400X

C-41: Agfa Agfacolor Optima 100, Agfa Agfacolor Optima 200, Agfa Agfacolor Optima 400, Fuji 8561 F250D, Fuji 8571 F500, Fuji Super Gold 100, Fuji Super Gold 200, Fuji Super Gold 800, Kodak 5245, Kodak 5095 EktaPress Plus 100, Kodak 5204 Kodacolor VR200, Kodak 5097 EktaPress 400, Kodak 5277 Vision 320T, and Kodak 5279 Vision 500T

These films were carried aboard the Space Shuttle to the ISS and returned to Earth after a period of 39, 63, and 120 days. These times were long enough to cause some radiation effects to be sensitometrically and digitally detectable while allowing the effects of the solar radiation to eventually plateau.

Two samples of each film type were given a set of exposures. These included a sensitometric exposure and a visual, bracketed-scene exposure of a controlled test setup. The control strips were stored at -18°C in the film vault at the Johnson Space Center (JSC).

We performed the following five steps to prepare the film for the test.

2.1 Sensitometric Film Preparation

The Precision Sensitometer Type 1-B was calibrated to a color temperature of 2850 K with a luminance of 0.685 lux. Each film type was exposed in the sensitometer using a 5500-K conversion filter. Films with ASAs (film speed rating) less than 200 were exposed at 1/50th of a second, while films with ASAs greater or equal to 200 were exposed at 1/100th of a second. After exposure, these films were rewound into their cassettes.

2.2 Standard Scene Imagery Preparation

A standard indoor scene was photographed and used as a subjective and qualitative reference. The scene consisted of three neutral-colored models of black, white, and gray; a Macbeth color checker card; three photographic mannequin busts with fair, medium, and dark skin tones; a gray scale; a resolution chart; three boxes covered with gold, black, and silver cellophane,

respectively; an American flag; and cue cards describing the exposure conditions. The props were arranged in a Macbeth Spectra Light II Color Matching Booth and illuminated with a daylight light source. The film was exposed with a Nikon F4 through a Nikon F/1.4 50-mm lens. Through-the-lens metering was used to determine the normal exposure. Three exposures were made: one each at the film's normal exposure rating, one underexposed by one stop, and one overexposed by one stop.

2.3 Packaging and Storage of Film Samples

The film was placed in a film can sealed with photographic tape approved for spaceflight. The storage conditions of the samples were maintained as best they could, considering the process required to get the film onboard *Mir* and back to JSC. Under ideal conditions, the film would have only been subjected to 18°C before on the ground and room temperature conditions for the test period in space. These test conditions were impossible to maintain due to manifesting considerations and may have had some impact on the results. Weight and volume were minimized as much as possible. We used four duplicate sets of film for this test:

- a. **Control Set**—This set was put in the JSC film vault after the sensitometry was put on the film and kept at 18°C.
- b. **39-Day Test Set**—This set was sent up on Progress 234 on April 6, 1997, and returned to JSC after 39 days on the ISS on STS-84.
- c. **64-Day Test Set**—This set was sent up on Progress 233 on November 20, 1996, and returned to JSC after 63 days on the ISS on STS-81.
- d. **120-Day Test Set**—This set was sent up on STS-81 on January 12, 1997, and returned to JSC after 132 days on the ISS on STS-84.

2.4 Film Processing

When the film samples were returned to Earth, all film processing of the test samples took place at the same time at JSC. The processors were certified "in-control" before processing any of the film samples. The film samples flown aboard *Mir* were processed together with the control samples. The negative films were processed in the Refrema Dip and Dunk type film processor and the positive films were processed in a Hostert Dip and Dunk type film processor.

2.5 Digital Processing

To analyze and correct the images digitally, we needed to scan the film on a Kodak 3570 scanner and archive it on CD-ROM. The scanned images were stored in the Kodak PhotoCD format so

that a variety of resolutions would be available for image correction and analysis. An accurate analysis required the scan of the gray card to have a resolution of 2k×3k. This is necessary for a requisite number of data points to produce a useful and meaningful frequency histogram of the pixel values.

3.0 EVALUATION CRITERIA

We used digital Fujix prints for the visual evaluation. These test prints included the control, unmodified, and digitally corrected images. A group of test subjects rated these prints for contrast, color rendition, and highlight and shadow detail. The test subjects determined the level of image degradation that occurred due to radiation. The actual test criteria are described in the Imagery Analysis section. The visual observer rating average determined the usefulness of the photographic image exposed to solar radiation. The visual observation average led to the elimination of ECN films and selection of four C-41 films and four E-6 films for further analysis. Eight films were selected for further study:

C-41

Agfa Optima 100

Fuji SG Plus 100

Fuji SG Plus 200

Kodak Kodacolor VR 200

E-6

Agfa Agfachrome RSX

Fuji Provia RDP2

Fuji RVP50

Kodak 5069 Elite

We measured the processed sensitometric film samples on a Macbeth densitometer and plotted them as density versus the logarithm of the exposure using MicroDense 4.0 software. We used the resulting characteristic curves to help evaluate the response to radiation of each type of test film flown. We made calculations of the sensitometric qualities of speed, average gradient, log exposure range, and useful density range of the film samples flown aboard *Mir*, and compared them to the control film samples.

We examined all eight of the above film types sensitometrically and digitally to determine the degree of image degradation due to radiation damage.

4.0 IMAGERY ANALYSIS

We divided the imagery analysis into three separate parts: visual evaluation, sensitometric evaluation, and digital evaluation. The visual evaluation used individuals with various backgrounds to determine which films could viably be used after exposure to radiation. The ranking that the test subjects gave the prints was averaged for each film type to give the “average

observer rating.” The eight films chosen by the average observer rating were subjected to further study.

We also quantitatively examined the images digitally since the imagery field will be moving toward the digital image, as opposed to the traditional photographic image. Using the digital evaluation, we determined relative grain size increase and that a radiated image can be partially restored (i.e., small color and contrast corrections). We also studied the effects of solar radiation on color.

4.1 Visual Evaluation

The test subjects ranked the 8×10 photographic prints on a scale of 1 to 5 on the three following criteria.

4.1.1 Image Contrast

Image contrast is a description of the rendition of the overall density range of the objects in the scene. Good contrast should neither expand nor contract the range of reflectance represented by objects in the scene. The brightest areas and darkest areas should display no apparent changes in their resolvable details and no losses due to too much or insufficient densities.

4.1.2 Color Rendition

Color rendition is the ability of a film to accurately capture and reproduce shades of color. Significant color shifts or changes in hue, or changes in color intensity or chroma, distort the imagery as it is portrayed in the final products. Some color shifts are not as serious as are others. Minor shifts to the red can enhance flesh tones and may not be objectionable. Other shifts, such as the yellowing of certain shades of green or the rendition of violet as purple, can be severe enough even when minor to preclude using a material for particular applications.

4.1.3 Shadow and Highlight Detail

Shadow and highlight detail are dependent upon the ability of the original film to capture the details present in the original scene under the exposure conditions present and on the manner in which the imagery is processed and reproduced. The dynamic range of the materials used for both duplication and printing must be great enough to overcome any losses of detail inherent in contrast reduction, should it occur.

4.2 Sensitometric Evaluation

The film was examined in the traditional, sensitometric method to see the effects of solar radiation on effective film speed, average gradient, log exposure range, and useful density range.

4.2.1 Film Speed

Photographic speed describes the inherent minimum sensitivity of a film to light under the normally specified conditions of exposure and development. A number derived from the sensitometric data contained in the characteristic curve represents film speed. The speed calculations for all film types conform to the International Organization of Standardization (ISO) specifications. The speed equations for color negative and color positive films follow:

Color negative film:
$$\text{ISO speed}_{\text{Color neg}} = \frac{1}{H_{\text{CN}}} * 1.5$$

Where H_{CN} equals an average red and green exposure in lux-seconds that produces a 0.15 increase in density relative to the base plus fog.

Color reversal film:
$$\text{ISO speed}_{\text{Color reversal}} = \frac{1}{H_{\text{CR}}} * 10.0$$

Where H_{CR} is an average of the two neutral exposures in lux-seconds that produce increases in the visual densities of 0.2 and 2.0 relative to the base plus fog.

4.2.2 Average Gradient

The average gradient is the slope of the line connecting the two critical points that define the useful limits of the characteristic curve. The critical points are defined as those values of exposure that are the maximum and minimum that still produce visually discernible changes in density. The portion of the sensitometric curve between the critical points encompasses the regions just beyond the ends of the straight-line portion.

4.2.3 Log Exposure Range

The log exposure range of a film is that range of exposures that produces densitometrically measurable changes in the film after development. The useful log exposure range is defined as that which is between the two critical points that delineate the boundaries of visually detectable change due to exposure.

4.2.4 Useful Density Range

The useful density range of a film is that which falls between the two critical points that also bound the useful exposure range and define the average gradient of the film.

4.3 Digital Evaluation

We evaluated the scanned samples to digitally quantify the damage caused by solar radiation. We chose the 120-day exposure samples of the eight films picked by the average observer rating for grain analysis. The digital evaluation of the film occurred in the following three sections: grain analysis, color shift analysis, and color layer analysis.

4.3.1 Grain Analysis

We used CISlab software to determine the grain increase between the control and 120-day samples. Exporting the pixel values from CISlab into Microsoft Excel created frequency histograms of the pixel values. The standard deviation of the pixel values in the gray patch was used as a digital method to determine grain size.

CISlab produced another digitally generated patch from the difference in the pixel values between the control sample and the 120-day sample. This provided a method of viewing just the induced “noise” from the films’ exposure to solar radiation. We generated a frequency histogram for this patch of induced noise to show the “image” formed from the films’ exposure to radiation.

4.3.2 Color Shift Analysis

We also examined the effect of radiation on the films’ ability to accurately record color, using the same 18% gray patch from the Macbeth ColorChecker that was used in the grain increase analysis. The values to determine brightness (L), red/green (a), and yellow/blue (b) were measured using Adobe PhotoShop. Three measurements were taken and averaged to find the reported L, a, and b values of each gray patch.

CISlab was used to help further analysis on the effects of solar radiation on color film by seeing the effects of radiation on each of the three color layers in film.

4.3.3 Color Layer Analysis

Each 18% gray patch was digitally divided into the three separate color layers that comprise color film. Once the gray patch was divided into the red/cyan, green/magenta, and blue/yellow layers, we found the average pixel value for the control, 39-day, 63-day, and 120-day samples for the separate color layers. We recorded the increase in average pixel values graphically to show any pattern that emerged as a result of the radiation exposure.

The grain increase as a function of exposure to solar radiation for each layer was examined in a similar manner. We graphically demonstrated the standard deviation in each color layer that we found for the control, 39-day, 63-day, and 120-day samples.

5.0 RESULTS

The overall results were similar to the results of DSO 318 and NASA TM-104817. The positive film had little damage to the useful portion of the characteristic curve and a much lower increase in grain size. The color layers of both the reversal and negative films reacted to the radiation in a similar manner, although the negative material was adversely affected to a greater extent.

We determined the grain size digitally, using pixel values of the scanned image. Ideally, since the patch off of the Macbeth ColorChecker is middle gray, the pixel values of the image would be approximately 127. This is due to the fact that the film has received a uniform exposure from the evenly lit surface of standardized color. However, when the image of the gray card is scanned, the fluctuation in the pixel values shows the non-image grain. We used the standard deviation of the pixel values in the gray patch to determine the amount of grain in both the control film and the flown film. Once the amount of grain for the control patch and the flown patch was determined, we ascertained the percent increase of grain due to the films' exposure to solar radiation.

When each of the color layers of the film was examined by means of average pixel values and standard deviation, we noticed an interesting correlation for a majority of the film types. The average pixel value and standard deviation were plotted as a function of the time. This showed that, as the film was exposed to more radiation, the rate of increase in the standard deviation of pixel values was much less than the rate of increase in the average pixel value. This implied that the grain size increase occurs until approximately 60 days of solar radiation exposure. After the 60-day period, a general fogging occurs in the image, exacerbating the grain appearance in the image.

Loss of color and contrast can be corrected in Adobe PhotoShop, but only to a certain extent. The apparent increase in grain size cannot be corrected and becomes readily apparent in the 120-day trial.

5.1 Comparison of Sensitometric Data for All Control and 120-Day Test Samples

The following tables provide data for comparison of test samples of film.

Table 1: Speed

Film Type (C-41)	Manufacture Rated ASA	Control Sample ASA	Test Sample ASA (120 day)
Agfa Optima 100	100	139.26	49.98
Fuji SG 100	100	149.22	65.14
Fuji SG 200	200	259.94	76.71
Kodak Kodacolor VR200	200	169.77	95.47

Film Type (E-6)	Manufacture Rated ASA	Control Sample ASA	Test Sample ASA (120 day)
Agfa Agfachrome RSX	50	49.86	59.26
Fuji Provia RDP2	100	79.94	85.54
Fuji RVP50	50	39.15	39.6
Kodak 5069 Elite	100	90.73	112.91

Table 2: Average Gradient

Film Type (C-41)	Control Sample Gamma	Test Sample Gamma
Agfa Optima 100	0.53	0.49
Fuji SG 100	0.53	0.41
Fuji SG 200	0.54	0.4
Kodak Kodacolor VR200	0.42	0.35

Film Type (E-6)	Control Sample Gamma	Test Sample Gamma
Agfa Agfachrome RSX	1.46	1.19
Fuji Provia RDP2	1.38	1.22
Fuji RVP50	1.57	1.32
Kodak 5069 Elite	1.36	1.11

Table 3: Log Exposure Range

Film Type (C-41)	Control Exposure Range	Test Exposure Range
Agfa Optima 100	2.75	2.03
Fuji SG 100	2.7	2.25
Fuji SG 200	2.65	2.15
Kodak Kodacolor VR200	2.49	2.27


Film Type (E-6)	Control Exposure Range	Test Exposure Range
Agfa Agfachrome RSX	2.78	1.69
Fuji Provia RDP2	2.12	1.89
Fuji RVP50	2.04	2.02
Kodak 5069 Elite	2.17	1.86

Table 4: Density Range

Film Type (C-41)	Control Density Range	Test Density Range
Agfa Optima 100	1.46	1
Fuji SG 100	1.43	0.93
Fuji SG 200	1.42	0.85
Kodak Kodacolor VR200	1.04	0.8

Film Type (E-6)	Control Density Range	Test Density Range
Agfa Agfachrome RSX	2.78	2.01
Fuji Provia RDP2	2.92	2.31
Fuji RVP50	3.2	2.66
Kodak 5069 Elite	2.96	2.06

5.2 Test Film Templates

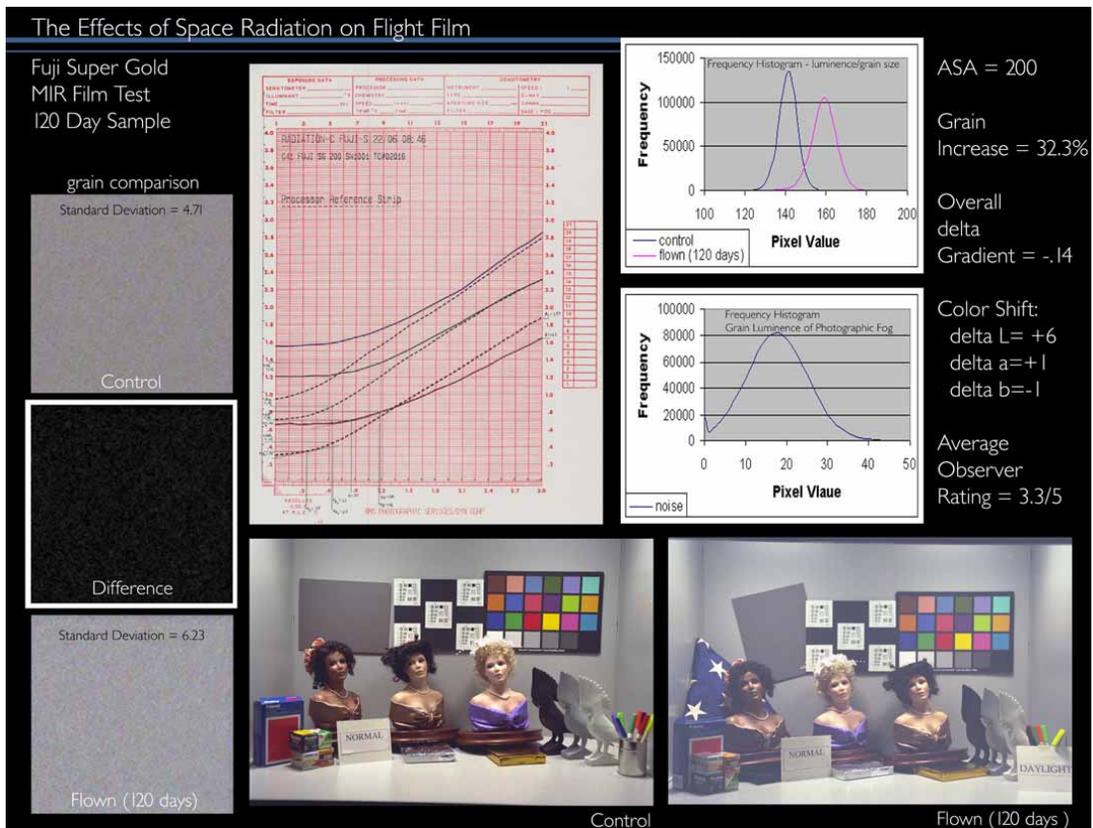

The Effects of Space Radiation on Flight Film


Kodak 5204 Kodacolor
VR200
MIR Film Test
120 Day Sample

grain comparison

Standard Deviation = 5.43



Control





Difference

Standard Deviation = 6.47




Flown (120 days)

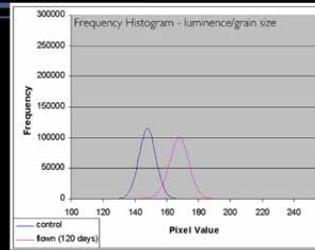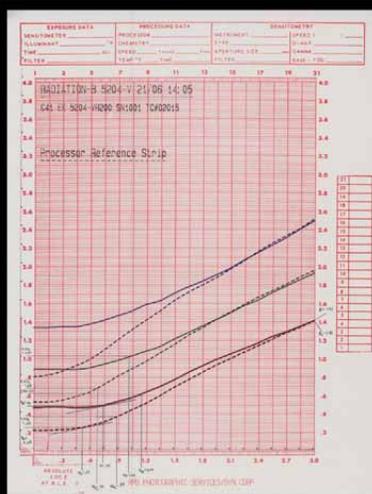

ASA = 200

Grain
Increase = 19.05%

Overall
delta
Gradient = -.11

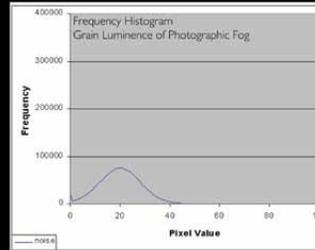

Color Shift:
delta L = +7
delta a = +2
delta b = +4

Average
Observer
Rating = 3/5



Control



Flown (120 days)

The Effects of Space Radiation on Flight Film


Agfa Optima
MIR Film Test
120 Day Sample

grain comparison

Standard Deviation = 5.16




Control





Difference

Standard Deviation = 6.56




Flown (120 days)

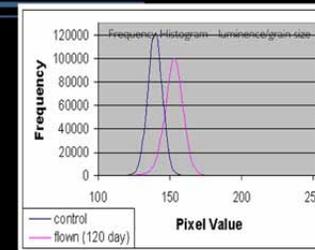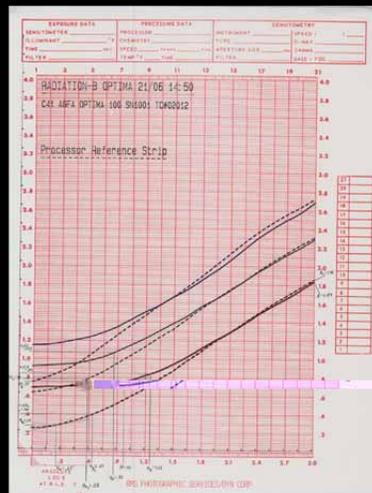

ASA = 100

Grain
Increase = 27.1%

Overall
delta
Gradient = -.04

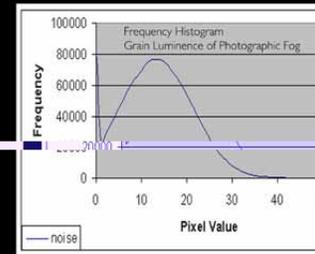

Color Shift:
delta L = +11
delta a = -5
delta b = +5

Average
Observer
Rating = 2.7/5






Control






Flown (120 days)




The Effects of Space Radiation on Flight Film Fuji Super Gold 100

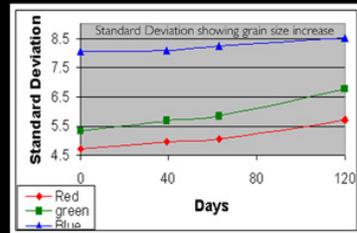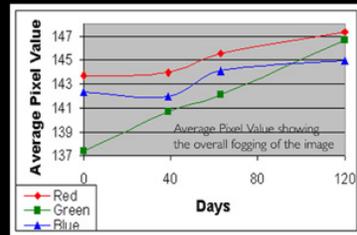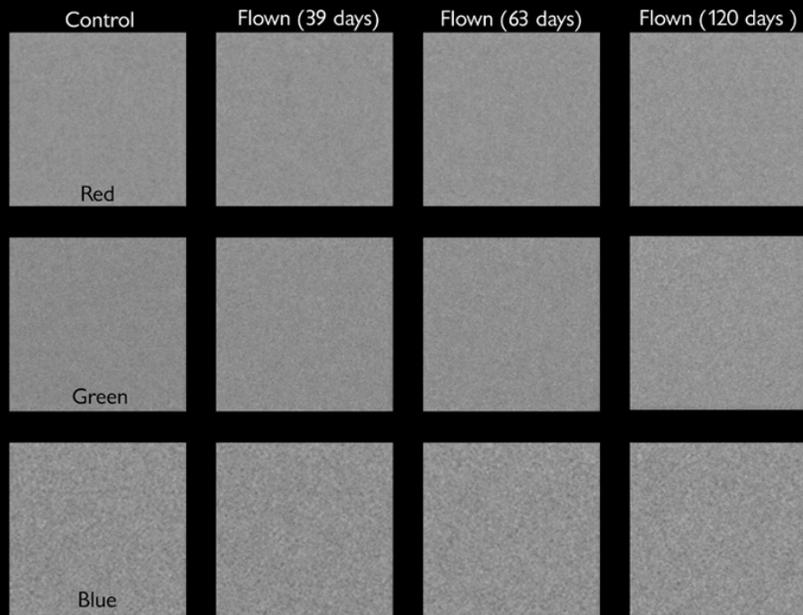




The Effects of Space Radiation on Flight Film Fuji Super Gold 200

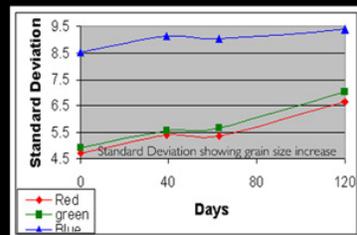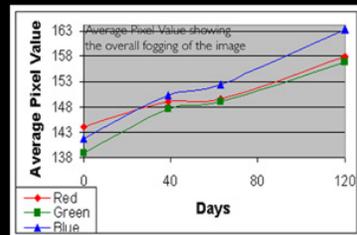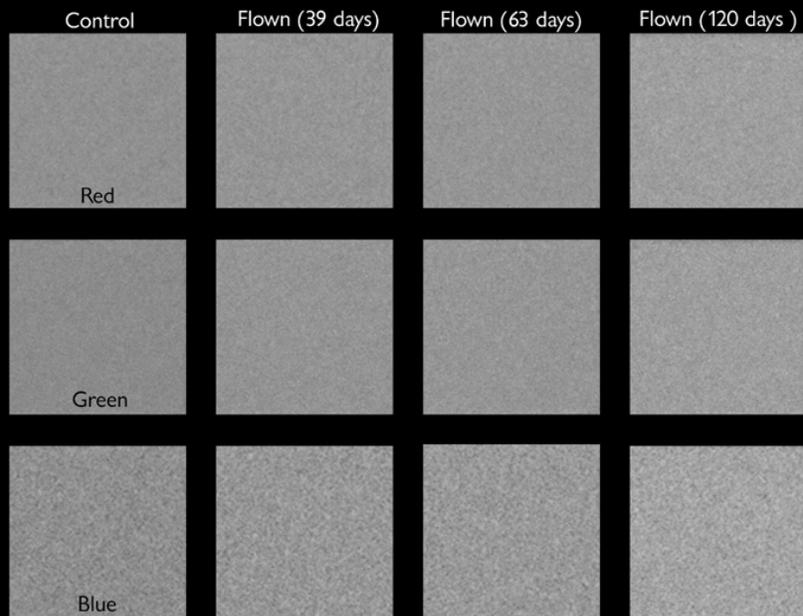


The Effects of Space Radiation on Flight Film
Kodak 5204 Kodacolor VR200

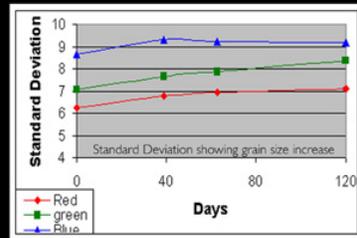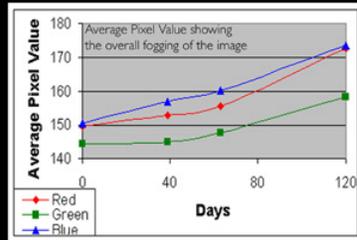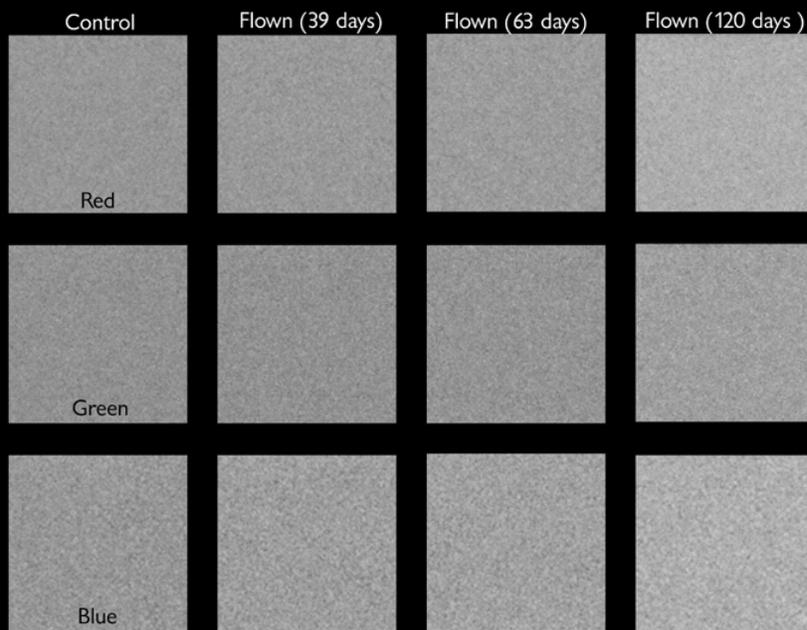

The Effects of Space Radiation on Flight Film
Agfa Optima 100

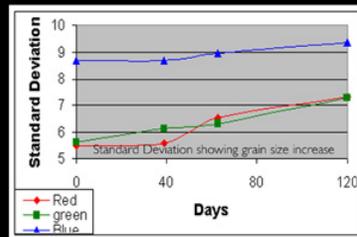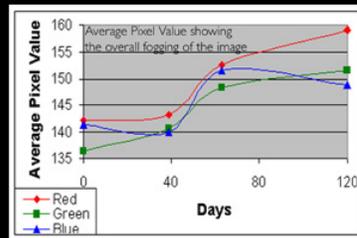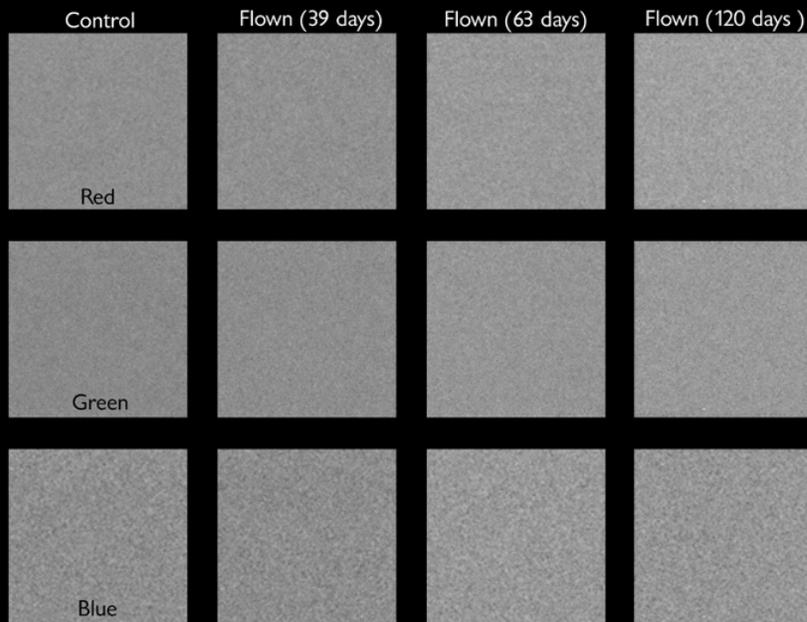


The Effects of Space Radiation on Flight Film - MIR Film Test
Fuji Super Gold ASA 100

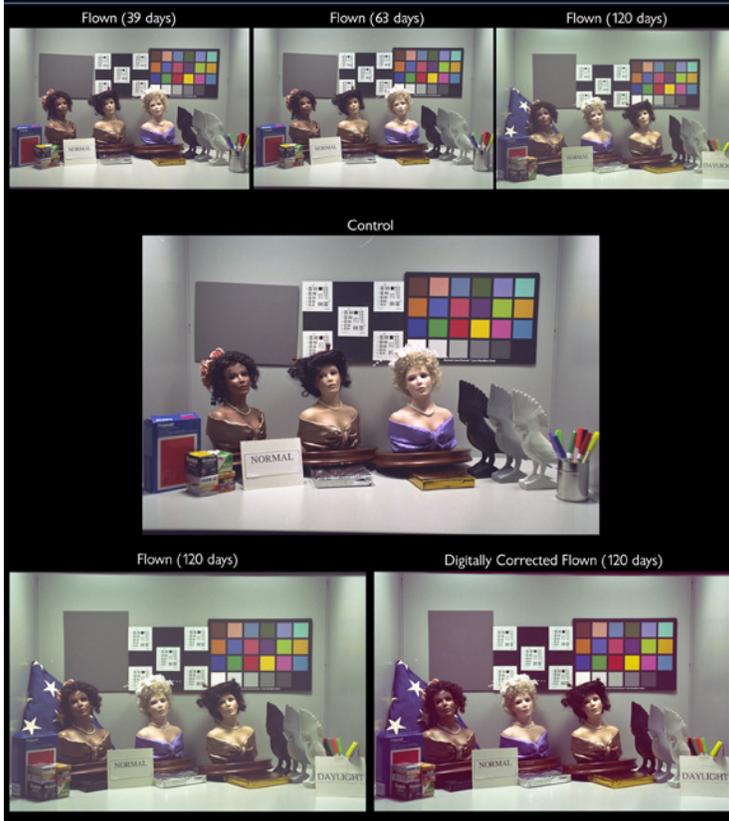


The Effects of Space Radiation on Flight Film - MIR Film Test
Fuji Super Gold ASA 200



The Effects of Space Radiation on Flight Film - MIR Film Test
Kodak 5204 Kodacolor VR 200

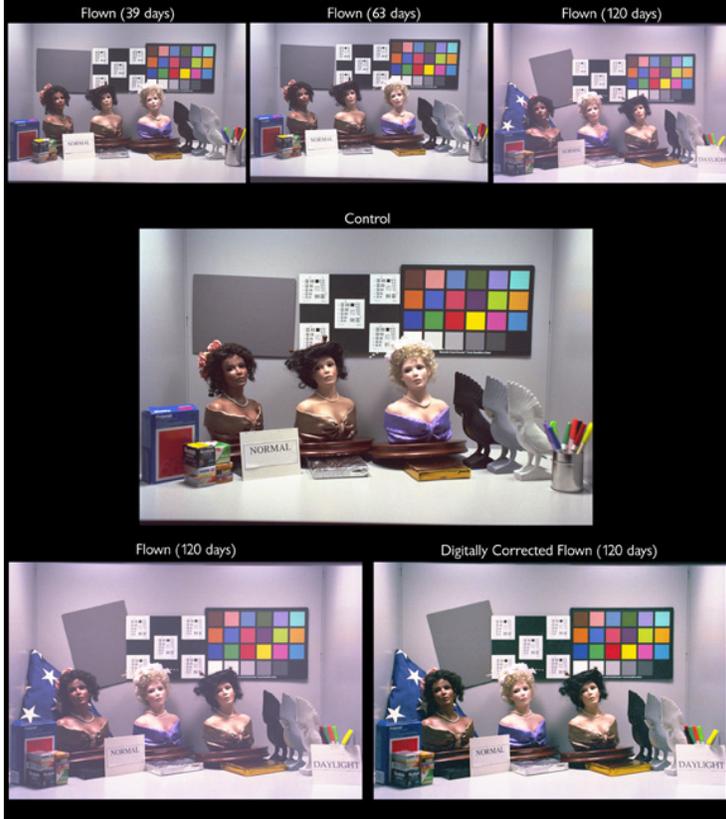

The Effects of Space Radiation on Flight Film - MIR Film Test
Agfa Agfacolor Optima 100

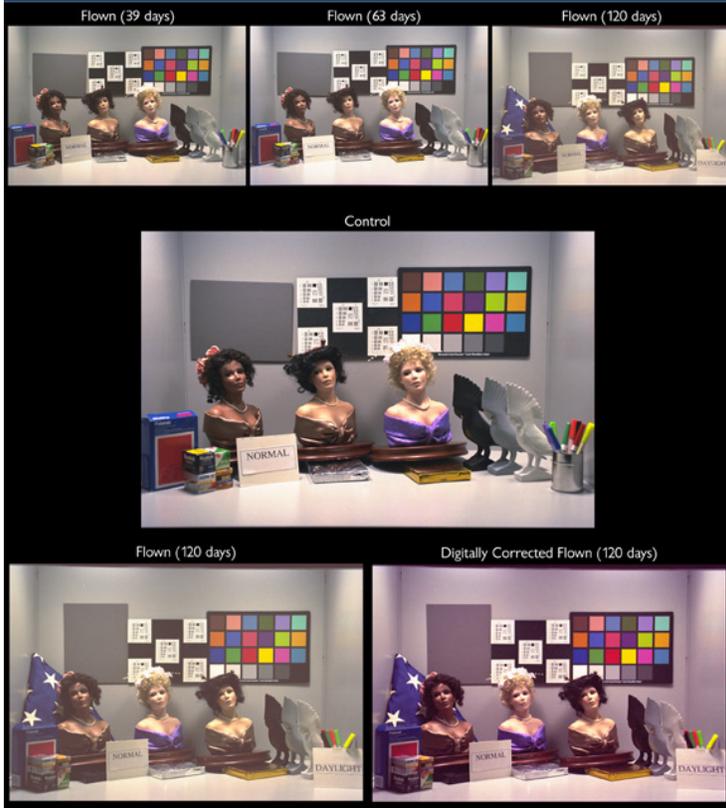

The Effects of Space Radiation on Flight Film

Agfa Agfachrome RSX
MIR Film Test
120 Day Sample

grain comparison



Standard Deviation = 2.88

Control

Difference

Standard Deviation = 3.31


Flown (120 days)

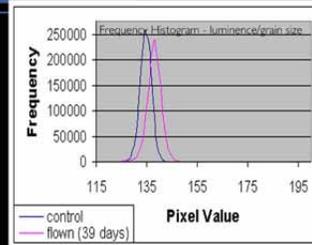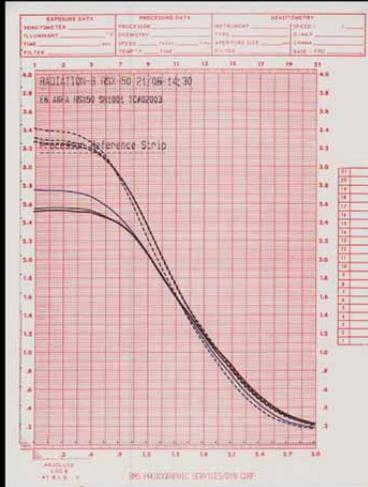

ASA = 50

Grain
Increase = 14.9%

Overall
delta
Gradient = -.27

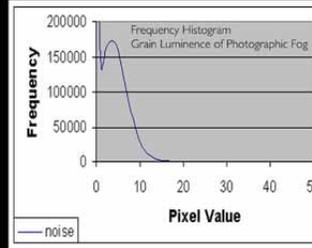

Color Shift:
delta L = -1
delta a = +2
delta b = -4

Average
Observer
Rating = 2.4/5



Control

Flown (120 days)

The Effects of Space Radiation on Flight Film

Fuji Provia RDP2
MIR Film Test
120 Day Sample

grain comparison



Standard Deviation = 2.26

Control

Difference

Standard Deviation = 3.00


Flown (120 days)

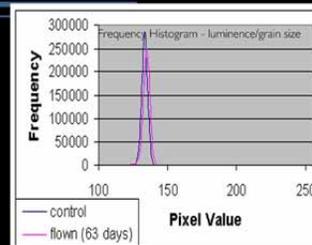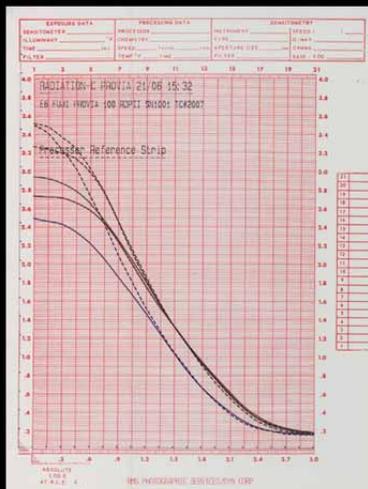

ASA = 100

Grain
Increase = 32.7%

Overall
delta
Gradient = -.16

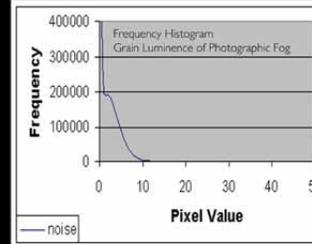

Color Shift:
delta L = 0
delta a = +4
delta b = -1

Average
Observer
Rating = 2.75/5



Control

Flown (120 days)

The Effects of Space Radiation on Flight Film

Fuji RVP50
MIR Film Test
120 Day Sample

grain comparison



Standard Deviation = 2.39

Control

Difference

Standard Deviation = 2.89


Flown (120 days)

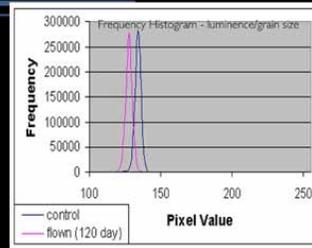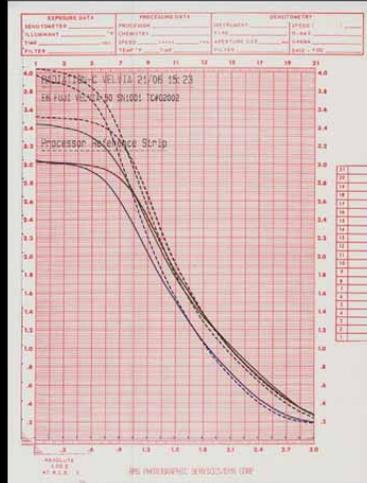

ASA = 50

Grain Increase = 20.9%

Overall delta Gradient = -.25

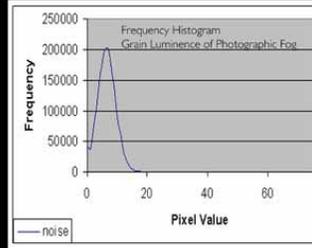

Color Shift:
delta L = -1
delta a = 0
delta b = -1

Average Observer Rating = 2.1/5



Control

Flown (120 days)

The Effects of Space Radiation on Flight Film

Kodak 5069 Elite
MIR Film Test
120 Day Sample

grain comparison



Standard Deviation = 2.54

Control

Difference

Standard Deviation = 2.99


Flown (120 days)

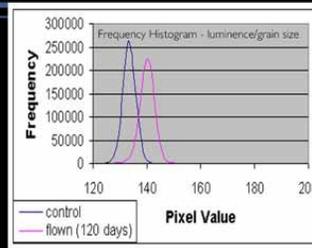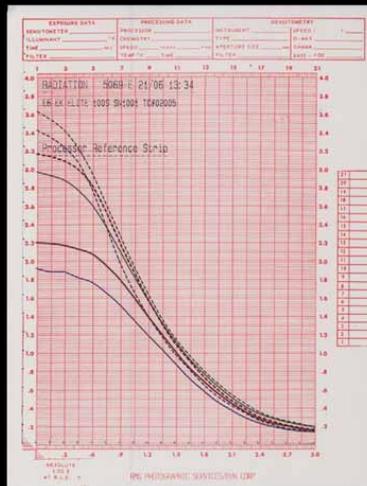

ASA = 100

Grain Increase = 17.7%

Overall delta Gradient = -.25

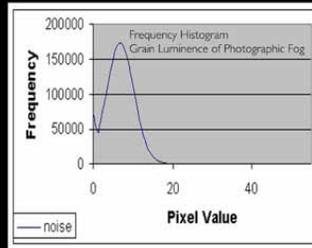

Color Shift:
delta L = -1
delta a = +6
delta b = -9




Average Observer Rating = 2.7/5






Control

Flown (120 days)




The Effects of Space Radiation on Flight Film Agfa RSX 50

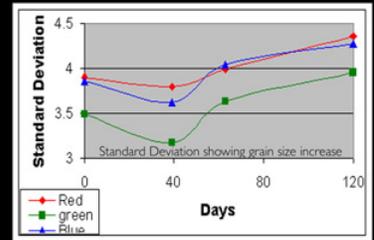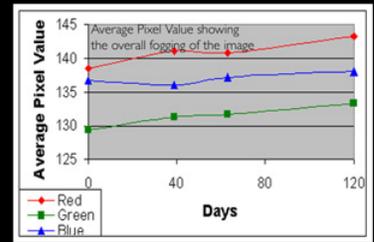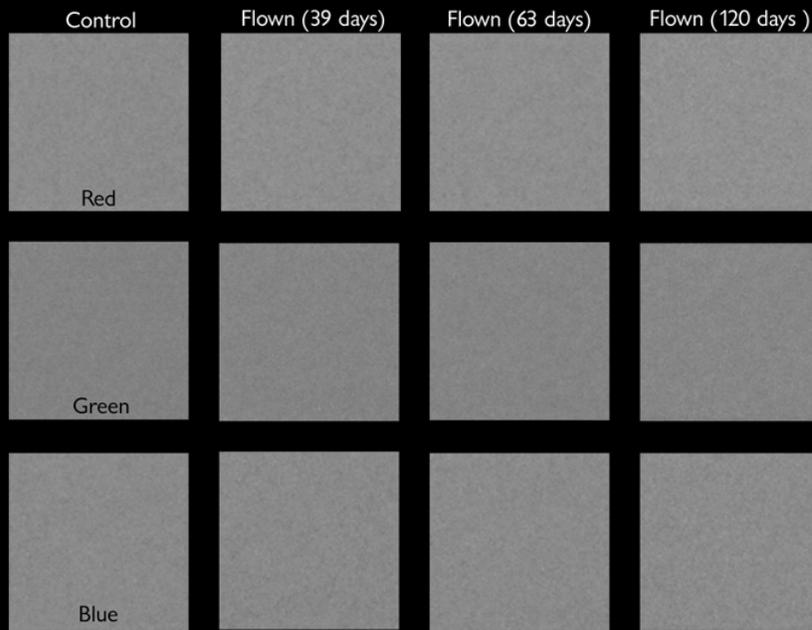




The Effects of Space Radiation on Flight Film - MIR Film Test Fuji RDP2 E-6

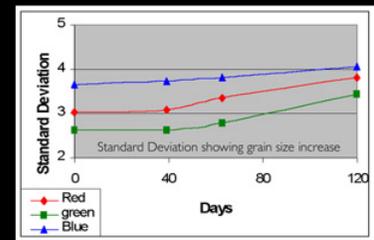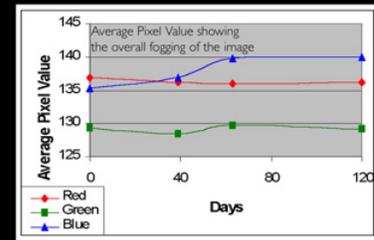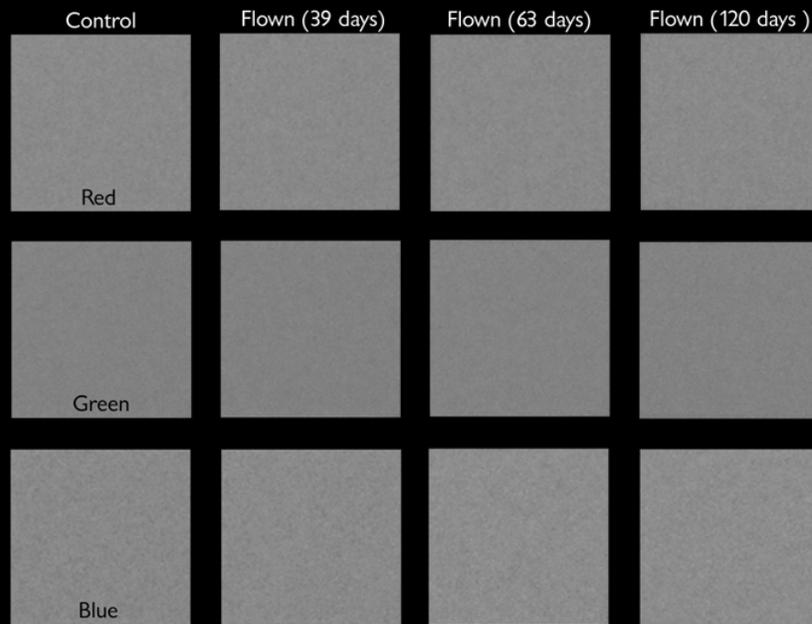

The Effects of Space Radiation on Flight Film
Fuji RVP 50

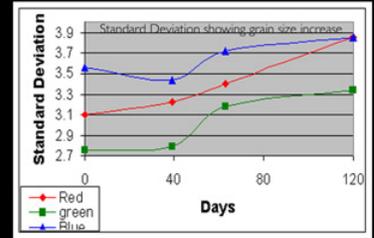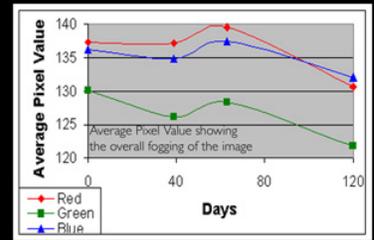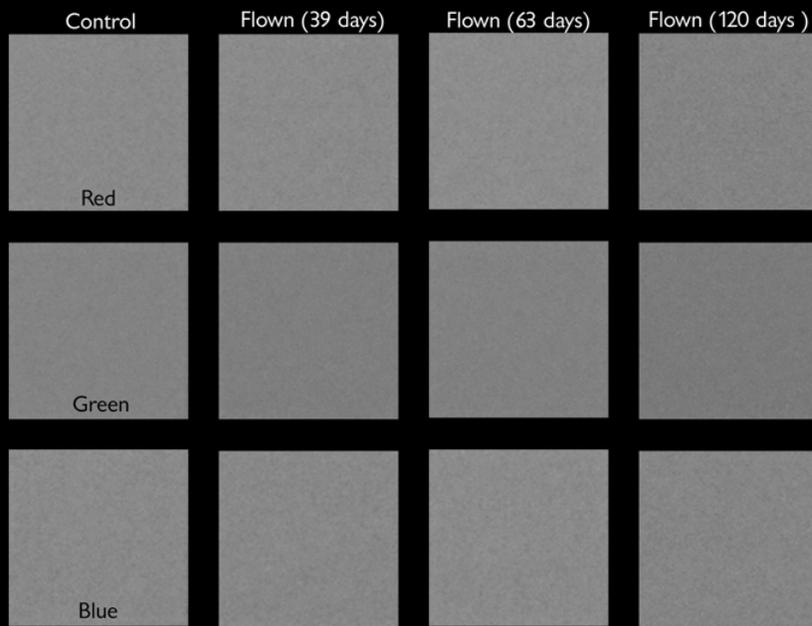

The Effects of Space Radiation on Flight Film
Kodak 5069

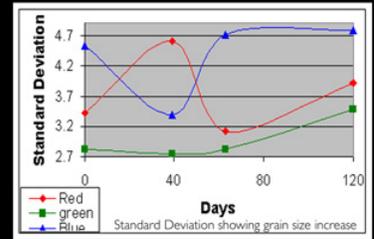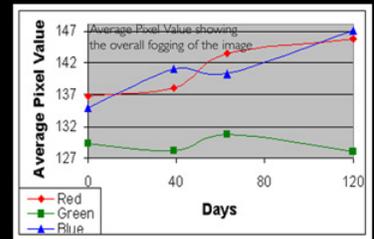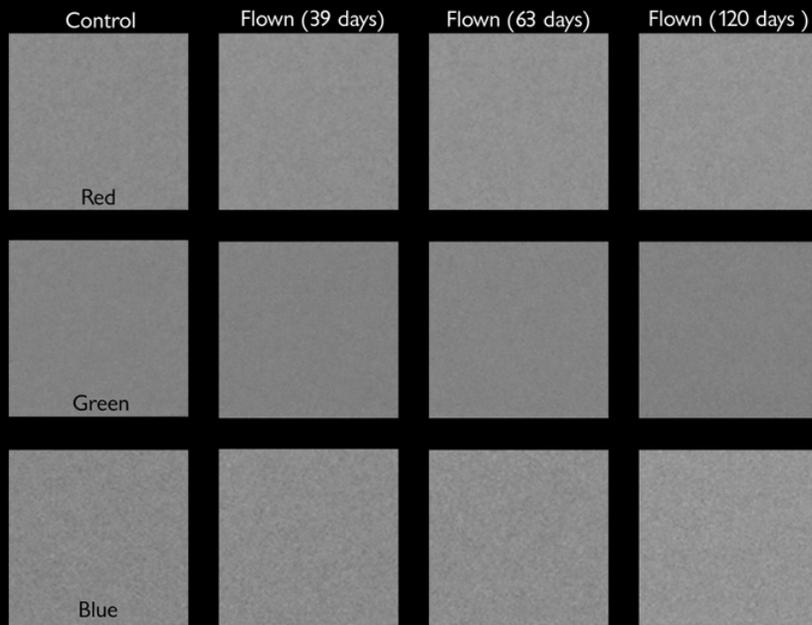

The Effects of Space Radiation on Flight Film - MIR Film Test
Agfa Agfachrome RSX 50




The Effects of Space Radiation on Flight Film - MIR Film Test
Fuji Provia RDP2 ASA 100



The Effects of Space Radiation on Flight Film - MIR Film Test
Fuji Velvia RVP 50



The Effects of Space Radiation on Flight Film - MIR Film Test
Kodak 5069 Elite 100S

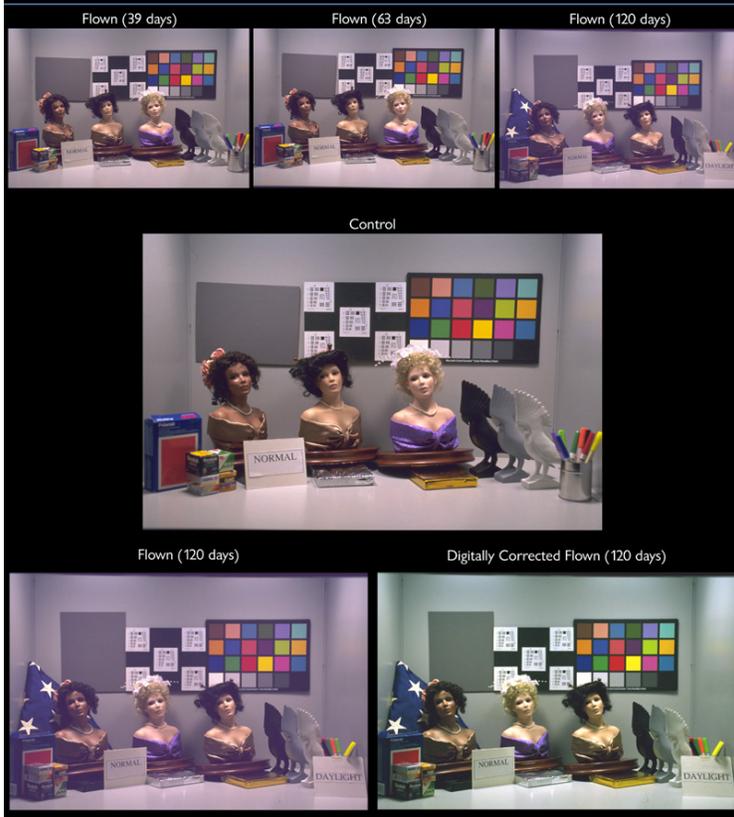

6.0 CONCLUSIONS

Typical ISS increments will be 90-120 days. This makes the 120-day results most realistic in determining which films will provide the best photographic results aboard the ISS. The 120-day samples were used to determine which films fell into the good, marginal, and unsatisfactory categories. Of the three different types of photographic films tested, only the motion picture films had results that were entirely unsatisfactory. IMAX motion picture films have been used in the past with excellent results. However, the films were only manifested on Space Shuttle missions that never exceeded 20 days or 200 nautical miles in altitude. The IMAX Corporation reviewed the test results and concluded that, for the best results, motion picture films used for IMAX productions on the ISS should only be used for short-duration missions (less than 20 days) as they have been in the past. The still photographic films (both negative and positive) used in the test mirrored the overall results from previous film tests. Positive films are visually less damaged from radiation than negative films and, in general, the lower-speed films for both types provide less graininess and better resolution than their high-speed counterparts. Of the still photographic films tested, eight films from all three manufacturing companies provided good results when scanned and digitally printed. No film was clearly better than the others in either the positive or negative category. The data tend to point toward one film in each category. However, when the test results were ranked from a purely visual standpoint, the films were too close to judge from anything but by personal choice. Resolution, saturation, varying lighting conditions, and numerous other variables makes it realistically impossible to state that one film type or manufacturer is the best and should be used for all still photographic imagery aboard the ISS. The test did conclude that, for the eight best films, it was possible to digitally correct the images close to their original image quality. The other films were not correctable due to the increase in film grain. In all cases, a photographic film should be chosen based on these test results, shooting conditions, and the final product to be produced.

REPORT DOCUMENTATION PAGE			Form Approved OMB No. 0704-0188	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.				
1. AGENCY USE ONLY (Leave Blank)	2. REPORT DATE October 2000	3. REPORT TYPE AND DATES COVERED NASA Technical Paper		
4. TITLE AND SUBTITLE The Effect of Radiation on Selected Photographic Films			5. FUNDING NUMBERS	
6. AUTHOR(S) Richard Slater, John Kinard, Ivan Firsov*				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Lyndon B. Johnson Space Center Houston, Texas 77058			8. PERFORMING ORGANIZATION REPORT NUMBERS S-869	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) National Aeronautics and Space Administration Washington, DC 20546-0001			10. SPONSORING/MONITORING AGENCY REPORT NUMBER TP-2000-210193	
11. SUPPLEMENTARY NOTES * Energia Space Corporation, Moscow, Russia				
12a. DISTRIBUTION/AVAILABILITY STATEMENT Available from the NASA Center for AeroSpace Information (CASI) 7121 Standard Hanover, MD 21076-1320 Category: 35			12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) We conducted this film test to evaluate several manufacturers' photographic films for their ability to acquire imagery on the International Space Station. We selected 25 motion picture, photographic slide, and negative films from three different film manufacturers. We based this selection on the fact that their films ranked highest in other similar film tests, and on their general acceptance by the international community. This test differed from previous tests because the entire evaluation process leading up to the final selection was based on information derived after the original flight film was scanned to a digital file. Previously conducted tests were evaluated entirely based on 8x10s that were produced from the film either directly or through the internegative process. This new evaluation procedure provided accurate quantitative data on granularity and contrast from the digital data. This test did not try to define which film was best visually. This is too often based on personal preference. However, the test results did group the films by good, marginal, and unacceptable. We developed, and included in this report, a template containing quantitative, graphical, and visual information for each film. These templates should be sufficient for comparing the different films tested and subsequently selecting a film or films to be used for experiments and general documentation on the International Space Station.				
14. SUBJECT TERMS photographic film, radiation, sensitometry, degradation, International Space Station, solar radiation			15. NUMBER OF PAGES 32	16. PRICE CODE
17. SECURITY CLASSIFICATION OF REPORT Unclassified	18. SECURITY CLASSIFICATION OF THIS PAGE Unclassified	19. SECURITY CLASSIFICATION OF ABSTRACT Unclassified	20. LIMITATION OF ABSTRACT Unlimited	